

---

# Research on Non-Reactive Brazed Connections of Steel/Ceramics

Yuqiang Liu<sup>1</sup>, Yan Zhang<sup>1,\*</sup>, Jianping Zhou<sup>1</sup>, Daqian Sun<sup>2</sup>, Hongmei Li<sup>2</sup>

<sup>1</sup>School of Mechanical Engineering, Xinjiang University, Wulumuqi, China

<sup>2</sup>Key Laboratory of Automobile Materials, School of Materials Science and Engineering, Jilin University, Changchun, China

## Email address:

Yanzhang4967@163.com (Yan Zhang)

\*Corresponding author

## To cite this article:

Yuqiang Liu, Yan Zhang, Jianping Zhou, Daqian Sun, Hongmei Li. Research on Non-Reactive Brazed Connections of Steel/Ceramics. *American Journal of Applied Scientific Research*. Vol. 9, No. 3, 2023, pp. 130-133. doi: 10.11648/j.ajars.20230903.16

Received: July 17, 2023; Accepted: August 7, 2023; Published: August 22, 2023

---

**Abstract:** The joining of dissimilar materials of ceramics and metals has been a hot research topic for both theoretical and practical applications at home and abroad. Connecting ceramics and metals together can combine the wear resistance, corrosion resistance and high temperature resistance of ceramics with the strong toughness of metals, becoming an ideal structural material and expanding the application fields of ceramics. The results of decades of research on ceramic and metal welding methods by countless scholars have shown that some of the joining problems have been solved, but the strength and heat resistance of ceramic/metal joints are still far from the requirements of using ceramic/metal joints. This paper reviews the current literature and practical applications, and after analysis, it is concluded that the effective methods for realizing ceramic-metal joints are mainly brazing, which has a very wide range of potential value in practical applications. However, these methods also have obvious drawbacks, leading to limitations in their own applications. For example, brazing generally requires a high surface quality of the workpiece, and this method of welding is only suitable for small workpieces and most lap joints, thus limiting its use in industrial production and making it unsuitable for high-temperature applications. On the other hand, inactive brazing permits effective ceramic/metal joining at high temperatures, which compensates to some extent for the disadvantages of brazing.

**Keywords:** Ceramic/Metal, Connections, Brazing, Inactive Brazing

---

## 1. Introduction

Nowadays, modern materials science and industry are continuing to evolve, thus placing higher demands on the performance of materials. A single material, due to its own limitations, has become difficult to meet the increasingly complex working conditions. Heterogeneous composite structural materials can combine the advantages of multiple materials to improve the overall performance of materials and also reduce the cost of materials to some extent [1]. Ceramics have superior resistance to corrosion and wear, as well as more stable thermal and chemical properties, etc., however, they have major limitations in terms of elongation, brittleness and workability [2, 3]. Steel has excellent mechanical properties with welding and processing properties and is inexpensive. However, its specific gravity is large and its

corrosion resistance is not outstanding enough [4, 5]. The use of ceramic/steel composite structural materials not only combines the excellent toughness and ductility of stainless steel, but also gives full play to the advantages of ceramic wear and corrosion resistance, forming a complementary advantage of the both.

## 2. Inactive Brazing

The wettability of the substrate should be considered during brazing. When joining a ceramic material to a metal, the filler metal must be sufficiently wetted and diffused into the substrate by melting at elevated temperatures [6]. This case is mainly about the wetting of the ceramic, because the filler metal which may wet the ceramic may also wet the metal. It is important to avoid mutual dissolution or overreaction between the filler metal and the substrate so that many brittle

compounds can not form, which would decrease the strength of the joint. By brazing ceramics to metal, it is possible to obtain reactive wetting, as with adhesives, diffusion and impregnating wets that are present in various joints. In the process of ceramic-to-metal joining, the liquefied metal attracts to the ceramic and metal interfaces, and gradually solubilizes and becomes chemically reaction, which then achieves the wetting and spreading of the substrates [7]. From a thermal-mechanical viewpoint, wetting during brazing involves the reduction of the free energy of the system (solid+liquid) after the exposure of the liquid metal to the solid substrate [8].

Metals' wettability is by no means the only factor to be considered in the ceramic-to-metal joining process. In special cases, the solder must fulfill its unique requirements. For example, high-temperature structural components require filler metals with high-temperature properties [9-11]. For sealing components, the filler metal must not contain significant amounts of Zn, Zn, Mg, Li, Bi, and other high-pressure components to avoid leakage [12, 13].

Currently, most popular filler metals do not wets ceramics and metals at the same time [14]. By adding reactive elements to metals that are traditionally used as fillers, wettability can be improved. For example, transition metal elements such as Ti, Zr, Hf, and V [15-17] are chemically active, react with metals (e.g., Fe, Co, Cu, Cr, Ni, and Ag), and have a strong affinity for a wide range of oxides, silicate materials, and ceramics. After these brazing filler metals are melted, the active elements in the molten metal diffuse into the ceramic and metal surfaces at high temperatures, interacting with them and causing chemical reactions or dissolution. Through the reaction products generated, the filler metal can effectively wet and diffuse into the ceramic surface. During the subsequent cooling process, the molten solder solidifies to reliably join the ceramic and metal [18].


From the above analysis, it can be concluded that the effective connection of ceramics to metals has the following three problems in the current research.

- (1) A variety of difficult and very brittle compounds can form easily at the interfaces of ceramics and metals. Ceramics and metals have different physical and chemical properties. Bond transformations and chemical reactions occur during the joining process. The formation of numerous oxide, carbide, nitride, silicide and multicomponent compounds takes place on ceramic-metal interfaces. While these compounds are typically hard and brittle, their complex distribution at the interface often leads to brittle fractures in the joints.
- (2) There is a large amount of residual stress at the interface between the ceramic and the metal. The modulus of elasticity and the coefficient of thermal expansion of the ceramic and the metal are changed. In the connection process and the subsequent cooling process, the thermal stress distribution is extremely uneven, and a large amount of residual stress is easily

generated. This leads to stress concentration at the connection interface and reduces the adhesive strength of the joint.

- (3) Lack of basic parameters that can be analyzed by numerical simulation. When ceramics are joined to metals, it is easy to form multiple composite layers. Although these composite layers are thin, they have a considerable effect on the joint properties. Due to the lack of room and high temperature parameters for the interfacial phases, numerical simulation analysis of the reactive reaction and the growth pattern of the reactive phases and calculation of the stress distribution are difficult. Consequently, numerical simulation analysis of ceramic-metal joints also becomes difficult.


To solve these problems scholars usually use hard brazing for steel/ceramic joints. Inactive brazing is based on the principle that under the action of high temperatures, the active elements within the base material diffuse through the molten solder to the surface of the other base material, resulting in a wetting effect. Therefore, it has obvious limitations on the base materials due to the lack of active elements in filler materials, so it is only suitable for ceramics containing active elements such as ZrO<sub>2</sub> ceramics and TiC ceramics [19]. J. C. Feng *et al.* [20] used AgCuZn braze alloy foil to join TiC cermet and steel. Ag, Cu solid solution and (Cu, Ni)+(Fe, Ni) phase were formed at the interface after holding at 850°C for 15 min. As shown in Figure 1a, the interface structure is TiC cermet/(Cu, Ni)/Ag(s.s.)/Cu(s.s.)/(Cu, Ni)/(Cu, Ni)+(Fe, Ni)/steel. The maximum shear strength of the joint was 120.7 MPa. YE. Dameng *et al.* [21] obtained firm joining between Ti(C,N)-based cermet and steel with Ag-Cu-Zn-Ni filler metal by vacuum brazing. As shown in Figure 1b, the interfacial reaction layer formed Ag-based solid solution, (Fe,Ni) solid solution, (Cu,Ni) solid solution and Cu<sub>5</sub>Zn<sub>8</sub>. The maximum shear strength of the brazing joint achieved 176.5 MPa. F. Z. Wang *et al.* [22] achieved good bonding between Ti(C,N)-based cermets and 17-4PH stainless steel by vacuum brazing, as shown in Figure 1c. It was found that with the increase of brazing temperature, the fracture of the joint began to occur on the brazing seam near the Ti (C,N)-based cermet, and then occurred inside the Ti(C,N)-based cermet. The fracture surface had obvious plastic deformation, indicating that the crack propagated with high resistance and the joint had high strength. The maximum shear strength of joint reached 690 MPa. M. F. Wu *et al.* [23] brazed Ti (C,N)-based cermets to 45 steel with copper foil interlayer. The results showed that the addition of copper foil can effectively release the residual stress of the joint. However, due to the dissolution of copper foil in the brazing process, as shown in Figure 1d. The chemical compatibility between the brazing filler metal and Ti (C,N)-based cermet was weakened, and the interface bonding force is reduced, resulting in a decrease in the strength of the joint. The bending strength of the joint reached 285 MPa.

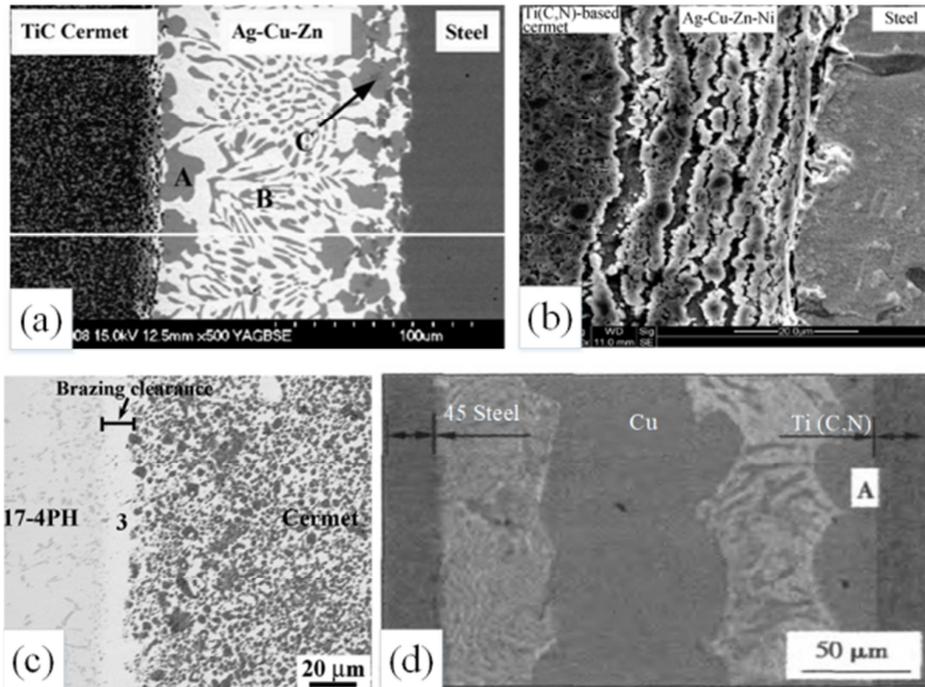

**Figure 1.** Inactive brazing of ceramics and metals: (a) TiC/AgCuZn/Steel. (b) Ti(C,N)/AgCuZnNi/Steel. (c) 17-4PH/BNi-2/Ti(C,N). (d) Ti(C,N)/AgCu/Cu/45Steel.

Singh M et al. [24] studied the effects of various solders containing Pd on the properties of YSZ/stainless steel joints. As shown in Figure 2a, there was a distinct interface layer in YSZ basement, unexpectedly, no Co was detected on YSZ or steel. As shown in Figure 2b, The interface of YSZ/steel was irregular which mean Fe, Cr element diffused. As shown in Figure 2c, There was no reaction layer in the steel/YSZ interface, forming silver-rich phase and rich-pass phase. However, there were Ag-rich and Cu-rich phases, also formed Ag-Cr and Ag-Pd phases in Figure 2d. The oxidation rates of 65Pd-35Co and 60Pd-40Ni joints are the fastest and slowest, respectively. The area of 59Ag-31Cu-10Pd and

5Ag-20Cu-15Pd brazed joints contains Ag-rich phase, Cu-rich phase and elements such as Zr, Y and Pd, which was the key to forming good metallurgical bonding. Kun-Lin Lin et al. [25] conducted a further research on YSZ/Ag-Cu-Pd/Steel brazed joint. As shown in Figure 2e, It was found that Ag particles precipitated within the Cu<sub>3</sub>Pd phase in 58Ag-32Cu-10Pd. However, a Fe(Cr) needle-like phase, instead of Ag particles, precipitated within the Cu<sub>3</sub>Pd phase in 65Ag-20Cu-15Pd, as shown in Figure 2f. The interlayer-YSZ interface formed SiO<sub>2</sub> and Ti<sub>3</sub>O<sub>5</sub> reaction products but no reaction products were found at the interlayer-steel interface.

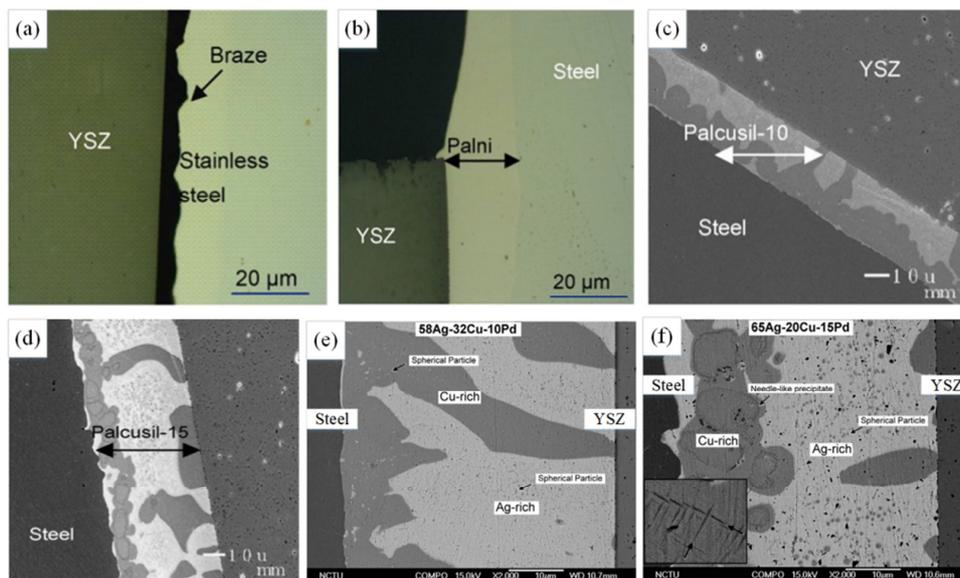

**Figure 2.** Microstructure of YSZ/stainless steel joint: (a) 65Pd-35Co. (b) 60Pd-40Ni. (c) 59Ag-31Cu-10Pd. (d) 65Ag-20Cu-15Pd. (e) 58Ag-32Cu-10Pd. (f) 65Ag-20Cu-15Pd.

### 3. Conclusion

A reliable link between ceramics and metals makes it possible to fully utilize the complementary performance and economic advantages of these two materials. The outstanding ceramic corrosion and high-temperature wear resistance takes full advantage of the good plasticity, ductility and high strength of metals. Although inactive brazing allows the joining of ceramics and steel, the requirements for the base material are high and require the base material to have active metal elements or modified treatment of the base material, which has major limitations. During inactive brazing, the active elements within the base material usually precipitate less and diffuse more slowly, which makes the connection of the joint more difficult.

---

### References

- [1] Zhang Y, Feng D, He Z, et al. Progress in joining ceramics to metals [J]. *Journal of Iron and Steel Research International*, 2006, 13 (2): 1-5.
- [2] Liu G, Zhang X, Yang J, et al. Recent advances in joining of SiC-based materials (monolithic SiC and SiCf/SiC composites): Joining processes, joint strength, and interfacial behavior [J]. *Journal of Advanced Ceramics*, 2019, 8: 19-38.
- [3] Hiraga H, Fukatsu K, Ogawa K, et al. Nd: YAG laser welding of pure titanium to stainless steel [J]. *Welding international*, 2002, 16 (8): 623-631.
- [4] Shuilin Rao. Research status of silicon nitride ceramic bearing technology for aero-engine [J]. *China Ceramic Industry*, 2020, 27 (03): 35-38.
- [5] Asthana R, Singh M, Sobczak N. The Role of Wetting and Reactivity in Infiltration of Ceramic-Metal Composites [J]. *Advances in Ceramic Coatings and Ceramic-Metal Systems: Ceramic Engineering and Science Proceedings*, 2005, 26: 248-261.
- [6] K. Nogi. The role of wettability in metal-ceramic joining [J]. *Scripta Materialia*, 2010, 62 (12): 945-948.
- [7] Y. V. Naidich, V. S. Zhuravlev, I. I. Gab, et al. Liquid metal wettability and advanced ceramic brazing [J]. *Journal of the European Ceramic Society*, 2008, 28 (4): 717-728.
- [8] R. M. do Nascimento, A. E. Martinelli, A. J. A. Buschinelli. Recent advances in metal-ceramic brazing [J]. *Ceramica*, 2003, 49: 178-198.
- [9] Floriana-Dana Börner, Max Schreier, Bing Feng, et al. Development of laser-based joining technology for the fabrication of ceramic thermoelectric modules [J]. *Journal of Materials Research*, 2014, 29 (16): 1771-1780.
- [10] B. Kuhn, E. Wessel, J. Malzbender, et al. Effect of isothermal aging on the mechanical performance of brazed ceramic/metal joints for planar SOFC-stacks [J]. *International Journal of Hydrogen Energy*, 2010, 35 (17): 9158-9165.
- [11] Huaping Xiong, Bo Chen, Haisheng Zhao, et al. V-containing-active high-temperature brazes for ceramic joining [J]. *Welding in the World*, 2016, 60: 99-108.
- [12] K. S. Weil, J. S. Hardy, J. P. Rice, et al. Brazing as a means of sealing ceramic membranes for use in advanced coal gasification processes [J]. *Fuel Guildford*, 2006, 85: 156-162.
- [13] F. Smeacetto, M. Salvo, M. Ferraris, et al. Characterization and performance of glass-ceramic sealant to join metallic interconnects to YSZ and anode-supported-electrolyte in planar SOFCs [J]. *Journal of the European Ceramic Society*, 2008, 28 (13): 2521-2527.
- [14] Z. Weltsch, A. Lovas. Alloying Effects on Wetting Ability of Diluted Ag-Based Melts on Ceramic Substrates [J]. *Materials Science Forum*, 2010, 659: 109-113.
- [15] Huaping Xiong, Bo Chen, Yu Pan, et al. Joining of Si<sub>3</sub>N<sub>4</sub> ceramic using PdCo(NiSiB)-V system brazing filler alloy and interfacial reactions [J]. *Progress in Natural Science Materials International*, 2014, 24: 61-67.
- [16] Alberto Passerone, Maria Luigia Muolo, Rada Novakovic, et al. Liquid metal/ceramic interactions in the (Cu, Ag, Au)/ZrB<sub>2</sub> systems [J]. *Journal of the European Ceramic Society*, 2007, 27 (10): 3277-3285.
- [17] A. Guedes, A. M. P. Pinto, M. Vieira, et al. Multilayered interface in Ti/Macor® machinable glass-ceramic joints [J]. *Materials Science and Engineering: A*, 2001, 301 (2): 118-124.
- [18] Weibing Guo, Zongyu She, Haitao Xue, et al. Effect of active Ti element on the bonding characteristic of the Ag(111)/α-Al<sub>2</sub>O<sub>3</sub>(0001) interface by using first principle calculation [J]. *Ceramics International*, 2020, 46 (4): 5430-5435.
- [19] Gorji A H, Simchi A, Kokabi A H. Development of composite silver/nickel nanopastes for low temperature joining of yttria-stabilized zirconia to stainless steels [J]. *Ceramics International*, 2015, 41 (1): 1815-1822.
- [20] Feng J, Zhang L. Interface structure and mechanical properties of the brazed joint of TiC cermet and steel [J]. *Journal of the European Ceramic Society*, 2006, 26 (7): 1287-1292.
- [21] Ye D, Xiong W, Zhang X, et al. Microstructure and shear strength of the brazed joint of Ti(C,N)-based cermet to steel [J]. *Rare Metals*, 2010, 29 (001): 72-77.
- [22] Wang F Z, Wang Q Z, Yu B H, et al. Interface structure and mechanical properties of Ti(C,N)-based cermet and 17-4PH stainless steel joint brazed with nickel-base filler metal BNi-2 [J]. *Journal of Materials Processing Tech*, 2011, 211 (11): 1804-1809.
- [23] Wu Mingfang, Chen Jian, Pu Juan, et al. Microstructure and mechanical properties of Ti (C,N) and 45 steel brazed joints [J]. *Welding Journal*, 2007 (12): 9-12+113.
- [24] Singh M, Shpargel T P, Asthana R. Braze oxidation behavior and joint microstructure in YSZ/steel joints made using palladium brazes for SOFC applications [J]. *Materials Science & Engineering A*, 2008, 485 (1-2): 695-702.
- [25] Lin K-L, Singh M, Asthana R. Interfacial characterization of YSZ-to-steel joints with Ag-Cu-Pd interlayers for solid oxide fuel cell applications [J]. *Ceramics International*, 2012, 38 (3): 1991-1998.