



# Techniques Reliability in Chromium-Rich Stainless Steels Failure Assessment

**Faraj Ahmed Emhmed Alhegagi**

The Department of Mechanical Engineering, Faculty of Engineering, Ben Walid University, Ben Walid, Libya

**Email address:**

Libyatat@yahoo.co.uk

**To cite this article:**

Faraj Ahmed Emhmed Alhegagi. Techniques Reliability in Chromium-Rich Stainless Steels failure Assessment. *Colloid and Surface Science*. Vol. 2, No. 4, 2017 pp. 125-129. doi: 10.11648/j.css.20170204.11

**Received:** June 19, 2017; **Accepted:** July 5, 2017; **Published:** August 18, 2017

---

**Abstract:** Specimens of duplex stainless steels 50:50 ferrite –Austenite were heat treated at 475°C for different times and pulled to failure. Fracture toughness testing was performed according to BS 7448, clip gauge, to monitor specimen displacement. In addition, the direct current potential drop (DCPD) technique was used to monitor the crack propagation. The Crack Tip Open Displacement (CTOD) was evaluated. Computational data, Shear model, were fit to the experimental ones. Discrepancy was observed between the experimental data and the computational ones. The model was able to expect the crack tip open displacement (CTOD), experimental data, only within a certain range of the material hardness. In addition, the direct current potential drop technique was more sensitive to detect the crack propagation process than that observed for the clip gauge. This work aims to study the fracture mechanism during cracking of duplex stainless steels.

**Keywords:** High Chromium Steels, Failure Mechanism, Toughness, 475°C Embrittlement

---

## 1. Introduction

High-chromium stainless steels normally become harder when they are held for long periods of time at temperatures in the range of 400-500°C. Embrittlement of duplex stainless at 475°C is accompanied by an increase in both the ferrite hardness and the ductile to brittle transition temperature [1]. Overall, the fracture toughness is reduced by the development of this phenomenon [2]. Duplex stainless steels (DSS) may be defined as a family of steels having a two phase, ferritic-austenitic or austenitic-ferritic, microstructure, the components of which are both stainless [3]. They combine good properties of ferritic steels alloyed with chromium and nickel, which provide excellent resistance to pitting and stress corrosion, and, in addition, from the mechanical point view a high degree of flexibility, resistance to fracture, good tensile strength. Accordingly, duplex stainless steels are attractive materials for oil and gas applications, particularly offshore where there is the added complication of corrosion by seawater [4]. Fracture of stainless steel parts can be contributed by their embrittlement which takes place during the process of thermal treatment.

### 1.1. Toughness Assessment

The crack initiation toughness (CTOD<sub>i</sub>), which characterizes the stable crack onset, is the parameter which best describes the intrinsic fracture toughness of the material. Fracture toughness testing of welds and ferritic steels in the brittle to ductile region often show a phenomenon called *pop-in* defined in the ASTM standard test method [5] as *discontinuity* in the load vs. clip gauge displacement record. The record of a pop-in shows a sudden increase in displacement and, generally, a decrease in load. Pop-in is a common feature of fracture testing in DSS. A graphical procedure based on the elastic compliance change during pop-in may be used for the fracture data analysis. The standard BS 7448 [6] for fracture toughness assessment assess each pop-in, in the load vs displacement draw, separately. The load drop,  $dn\% F$ , at the each pop-in is measured according to the following equation.

$$d_n \% F_1 = 100 \left[ 1 - \frac{D_1}{F_1} \left( \frac{F_n - Y_n}{D_n - X_n} \right) \right] \% \quad (1)$$

where n is the number of the considered popin i.e. 1st, 2nd, 3rd etc.  $Y_n$  and  $X_n$  are the resultant change in load and COD respectively. The other parameters in equation (1) are defined

in the BS 7448 [6]. Pop-ins having load drop value less than 5% are ignored. If higher, the ratio  $F_{max}/F_{pop-in}$  is used to assess the validity  $F_{pop-in}$  for the calculation of KIC. If this ratio is higher than 1.1, the  $F_{pop-in}$  then is considered to be invalid for the calculation of KIC and should be used for CTOD assessment instead. Fracture toughness testing can be performed using a clip gauge to monitor specimen displacement. In addition, the direct current potential drop (DCPD) technique is used to monitor the crack propagation. In this technique a constant D. C current passes across the tested specimen. An electric field is produced and distributed across the specimen material. As the crack propagates, the flow area is reduced which causes a change in the potential distribution. Crack propagation therefore gives a measurable change in the voltage measured across the crack. Good sensitivity could be obtained if the two inputs were located close to the cracking plane.

### 1.2. Stress Intensity Parameter

Curry [7] combined the model proposed by Ritchie and Knott [8] with the analysis of the stress field and obtained the relationship between fracture toughness ( $K_{IC}$ ) and the critical distance for cleavage fracture as follows:

$$K_{IC} = \beta^{\frac{(N+1)}{2}} X_0^{\frac{1}{2}} \frac{\sigma_f^{\frac{N+1}{2}}}{\sigma_y^{\frac{N-1}{2}}} \quad (2)$$

where  $N$  and  $\hat{\alpha}$  are material constants. The critical tensile stress model was proposed [8] to apply for materials where inclusions and carbide particles serve as crack nuclei. Plastic deformation easily cracks those particles and fracture is a propagation-controlled process. This model is not applicable for duplex stainless steels since it is clean material with a few inclusions, and crack initiation is difficult i.e. fracture in DSS is a crack initiation controlled process. Accordingly the critical shear stress model for fracture of duplex stainless steels was more convenient. In this model [9], the fracture criteria assume critical shear stress ( $\hat{\sigma}_f$ ) acting over a critical distance ( $X_0$ ). That is

$$\sigma_{12} > \tau_f \text{ and } X < X_0 \quad (3)$$

and

$$K_{IC} = \beta^{\frac{(N+1)}{2}} X_0^{\frac{1}{2}} \frac{\tau_f^{\frac{N+1}{2}}}{\sigma_y^{\frac{N-1}{2}}} \quad (4)$$

$$CTOD_{init} = 0.717 \frac{K_{IC}^2}{E\sigma_y} \quad (5)$$

$$\tau_f = \tau_i + \tau_s \quad (6)$$

and

$$\tau_s = \frac{G}{2\pi(1-\nu)} \sqrt{\frac{3.67b}{D}} \quad (7)$$

Where

$\tau_i$  is the friction stress.

$\tau_s$  is the critical shear stress for crack nucleation.

$G$  is the shear modulus.

$\nu$  is Poisson's ratio.

$b$  is the Burger's length.

$D$  is the length of dislocation pile-up.

## 2. Experimental Procedure

The aim of these experiments was to investigate the interaction between the microstructure and the propagation of stable cracks i.e. the effect of microstructure on the fracture toughness (CTOD) of duplex stainless steels. In addition, the fracture mechanism was to be studied to determine if any transition took place.

### 2.1. Materials

The material chemical composition is shown in table 1. Two phases were present in the as-received microstructure with 50:50 ratio; the ferrite phase and austenite phase as illustrated in Figure 1. This microstructure was observed to be free of sigma phase and with a hardness of 258Hv. Specimens were machined according to BS 7448 [6] as straight notch compact tension (CT) specimens. In order to introduce a sharp crack in front of the notch tip, specimens were fatigued for a few millimeters. Specimens were then heat treated, to introduce brittleness to the ferrite phase, at 475°C for the following aging times 2h, 5h, 13h, 24h, 49h, 72h, 166h, and 118h. That was in order to obtain different levels of hardness. Finally, specimens were allowed to air-cool to room temperature.

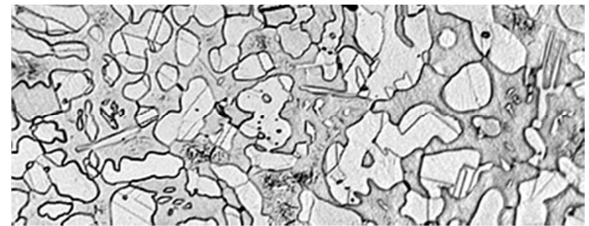


Figure 1. The as-received microstructure 50:50 ferrite (gray) – austenite (White).

Table 1. The chemical composition of the as-received materials.

| Element | Wt %  |
|---------|-------|
| C       | 0.02  |
| Si      | 0.22  |
| Mn      | 0.58  |
| P       | 0.021 |
| S       | 0.001 |
| Cr      | 25.12 |
| Mo      | 3.55  |
| Ni      | 6.90  |
| W       | 0.54  |
| Cu      | 0.59  |
| Fe      | Bal   |

## 2.2. Failure Assessment

Failure testing was performed according to BS 7448 using a clip gauge to monitor specimen displacement. In addition, the direct current potential drop (DCPD) technique, of constant current of 10A, was used to monitor the crack propagation. A millimeter was connected to monitor the potential, typically 1.36mV, at the test start across the specimen. During loading, the load vs. time and potential change across the specimen were recorded by a connected chart recorder. That was to determine the load when the DCPD was observed to change by a fixed amount, representative of a critical amount of crack propagation. Another chart recorder, connected to the clip gauge, was used to record the relationship between the load and COD during loading stage i.e. Pop-in. Specimens finally were loaded to failure at 1mm/min cross head speed. Data analysis was carried out according to BS 7448 first for pop-in and KIC measurement validity. Each pop-in was assessed initially according to equation (1). Pop-ins having  $\Delta n\%$  F value less than 5% were ignored. A line of 5% less slope than that of the elastic line was drawn according to BS 7448. The values of FQ, Fmax and FQ/Fmax were calculated. For any pop-in, FQ was the point at which the line of 5% intersects the load vs. COD curve. This means that if the concerned pop-in took place at a force higher / lower than the measured FQ, then F at which the concerned pop-in took place was considered to be FQ. The load Fmax was taken as the maximum force reached during the specimen loading. The resulted change in load and COD due to pop-in were considered as  $\Delta Y_n$  and  $\Delta X_n$  respectively in equation (1). The FQ/Fmax ratio was used to assess the validity of FQ the calculation of KIC. If this ratio was higher than 1.1, then the FQ was considered to be invalid for the calculation of KIC value. For valid pop-ins, CTOD value was calculated for KIC measurement, according to the following [6]:

$$CTOD = \left[ \frac{F}{B W^{0.5}} f' \left( \frac{a_0}{W} \right) \right]^2 \left[ \frac{(1 - \nu^2)}{2 \sigma_{YS} E} + \frac{0.46(W - a_0) V_p}{0.46W + 0.54a_0 + (C - W) + Z} \right] \quad (8)$$

Where:

F the load at pop-in/fracture.

$\sigma_{ys}$  the yield stress.

E Young's modulus.

$V_p$  the plastic component at the pop-in/final fracture considered.

B,  $a_0$ , W and C as defined in Figure 1

Z the Knife edges thickness.

$\nu$  Poisson's ratio was taken as 0.3, E as 203 GPa. The yield stress ( $\sigma_{ys}$ ) was taken as the 0.5% proof stress.

For the direct current potential drop technique the force  $F_{dcpd}$ , at which a stable crack growth took place, was determined from load vs. dcpd chart obtained, considering

the dcpd increase. The dcpd increase for the determination of  $F_{dcpd}$  was selected with sensitivity gives a crack growth increment of 1%. The voltage change equivalent to 1% increase in the crack length was calculated according to the following equation (ASTM E1290) [5];

$$\frac{V}{V_r} = A_0 + A_1 \left( \frac{a}{W} \right) + A_2 \left( \frac{a}{W} \right)^2 + A_3 \left( \frac{a}{W} \right)^3 \quad (9)$$

$$0.24 \leq \frac{a}{W} \leq 0.7 \quad (10).$$


Where;

V = the measured electric potential difference (EPD) voltage,  $V_r$  = the reference crack voltage corresponding to  $a/W = 0.241$ , a = the crack size, W = the specimen width,  $A_0 = 0.5766$ ,  $A_1 = 1.9169$ ,  $A_2 = -1.0712$  and  $A_3 = 1.6898$ . Voltage change of  $0.006 \pm 0.001$  mV was observed to be equivalent to 1% increase in the crack length. The  $CTOD_{dcpd}$  value was calculated using equation (8). The term  $V_p$  is the plastic component of the equation. The tested specimens were of 0.5% proof stress in the range of 829-946 MPa. Fracture surfaces of three specimens of different proof stress i.e. 829, 841, and 862 KN/mm<sup>2</sup> were examined using (SEM). That was in order to examine any transition in the fracture mechanism as the proof stress goes to a lower value. The fracture mechanism was expected to change from brittle fracture to ductile failure with decreasing hardness.


## 3. Results and Discussion

The specimens hardness and yield stress were observed to increase with ageing time. This may be attributed to 475°C embrittlement which took place in ferrite. Specimen proof stress that was selected was for 0.5% strain, since the 0.1% and 0.2% proof stress showed significant scatter compared to the 0.5% proof stress. This scatter may be due to the early yielding and the work hardening of the softer austenite, giving a non-linear behavior at low strains. Near the crack tip, the critical tensile stress for crack propagation is already satisfied. Consequently, the cracking criterion is nucleation-controlled. That is by availability of nucleation sites such as twins, Figure 2, ahead of the crack tip characterized by a critical distance, which in turn depends on ferrite grain size. The standard BS7448 [6] was followed to check specimen validity for fractured toughness assessment by direct determination of  $K_{IC}$ . In most cases, specimens were invalid for  $K_{IC}$  measurement as. The crack tip opening displacement fracture toughness (CTOD) was therefore used. The fracture toughness for stable crack growth ( $CTOD_i$ ) decreased with increasing specimen proof stress Figure 3. This may be understood as a result of 475°C embrittlement as reported in literature. Dislocation movement is retarded by both factors increasing ferrite cleavage, and lower fracture toughness is predicted. The fracture toughness ( $CTOD_i$ ) data showed agreement between the two techniques for higher proof stress Figure 3. At lower yield stress, the two techniques showed

discrepancy in the fracture toughness data. For proof stress value below 850MPa, higher CTOD values were observed using BS7448 [6]. The interpretation is that stable crack growth was detected by dcpd technique but not by BS7448. This is since detection of stable crack growth by dcpd technique is subject to achievement of 1% increase in crack length, equivalent to  $0.006 \pm 0.001$  mV voltage increase, regardless of specimen behavior during loading. Consequently, higher (CTODi) values using BS7448 technique are expected.

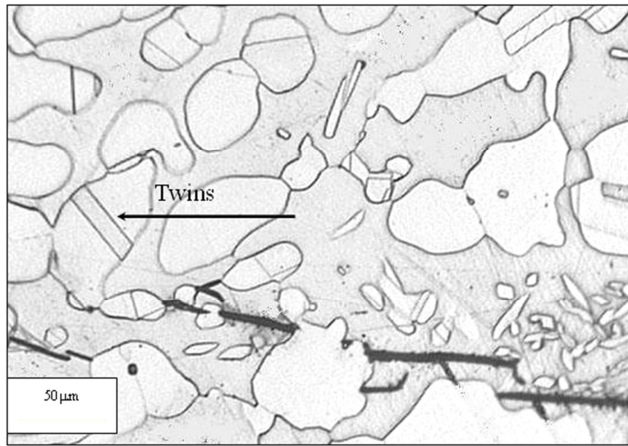


**Figure 2.** Twins observed ahead of the crack tip for specimen aged at 475°C for 13h.

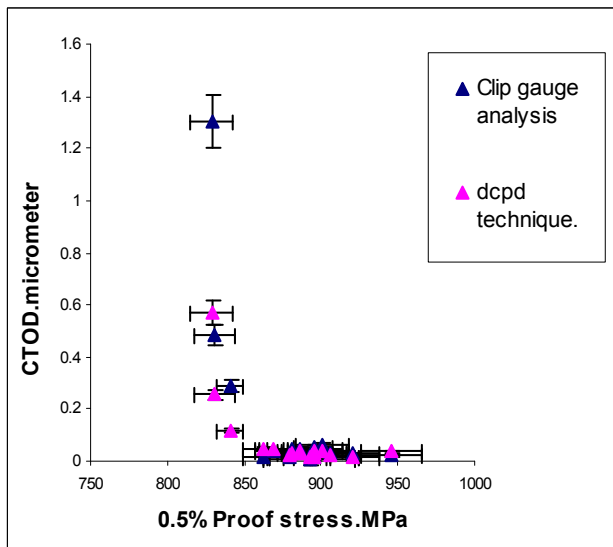

**Figure 3.** The CTOD vs. yield stress observed (CT) specimens tested for fracture toughness.

For specimen aged for longer ageing times, higher proof stress, the CTOD data was in agreement using the two techniques. This may be because that ferrite cleavage, Figure 4, is encouraged by embrittlement of the ferrite. As demonstrated, the tendency for ferrite cleavage increases with ageing time. This will encourage unstable brittle fracture. The two procedures are equivalent only when single pop-ins are assessed. This implies that CTODi

measurement by dcpd monitoring produces a better measure of toughness in small specimens than BS7448 clip gauge method. In Figure 4, the data obtained was fitted to the critical shear stress model for brittle fracture in duplex stainless steels. The elastic modulus value was 200GPa,  $\hat{\alpha}=0.59$  and  $N=13$  taken from Rice and Johnson [10].

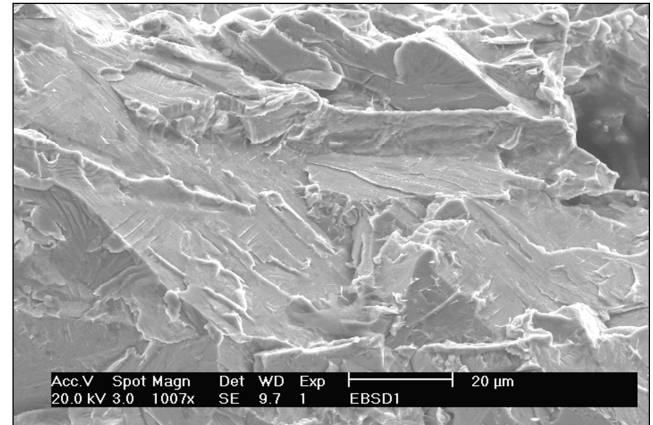

**Figure 4.** SEM for ferrite cleavage. Sp. Aged for 100h at 475°C tested at  $K_{applied} = 75 \text{ MPa}\sqrt{\text{m}}$ .

The critical shear stress for nucleation ( $\hat{\sigma}_f$ ), depends on specimen yield stress, and was estimated from the data reported by Marrow et al. [11]. The critical distance, ( $X_0$ ) in equation (5), was selected as 20μm to fit the experimental data to the critical shear stress. As a physical meaning, the critical distance ( $X_0$ ) represents the availability of twins, for crack initiation, a head of the crack tip. The measured grain size, equivalent to the distance between the centers of two adjacent austenite grains, was 50μm. The experimental data was not in good agreement with the model. This implies that 20μm, as a critical distance ( $X_0$ ), is not a good value for fitting the experimental data to the critical shear stress model. As illustrated in Figure 2, the obtained fracture toughness data (CTODi) was in good agreement with the critical shear model only at relatively higher proof stresses i.e. proof stress higher than 850MPa. Below this proof stress value, the (CTODi) value obtained, either using BS7448 or dcpd technique, was higher than that predicted by the model. This is may due to that a transition in fracture mode which took place at/near this proof stress value. It is well documented that 475°C embrittlement may change the cracking mode from ductile failure to brittle cleavage [11]. Brittle fracture nucleation is related to deformation twinning. Below the proof stress of 850MP, higher (CTODi) value was not predicted by the critical shear stress model. This is attributed to the transition being not taken into account by the critical shear stress model. Below the transition, the critical tensile stress for crack propagation may be satisfied i.e. already exceeded near the crack tip, but not the critical shear stress for crack nucleation i.e. crack nucleation by deformation twinning is more difficult to satisfy than the condition for crack propagation. Brittle fracture of embrittled DSS can be modeled using the shear stress model only if ferrite fails by cleavage. Ornek et.al [12] investigated the fracture of stainless

steels 2205 in chloride-containing deposits i.e atmospheric-Induced stress corrosion cracking (AISCC). They aged the specimens for different time 10-255 h testing them in aggressive environment with different concentrations of chlorides. They found the specimens hardness increased with the ageing time at 475°C. This is in good agreement with the results obtained in this work. The fracture mode they observed was the ferrite and austenite dissolution. This can be attributed to the action of environment used for testing specially at high concentrations of chlorides i.e. 15  $\mu\text{g}/\text{cm}^2$ , 247  $\mu\text{g}/\text{cm}^2$ , and 2856  $\mu\text{g}/\text{cm}^2$ . Accordingly, the fracture mode and mechanism will be affected and differs compared to the one observed at the present work. The fracture mechanism of SCC and brittle fracture, in air, should be the same in the case where ever ferrite cleavage takes place due to ageing.

## 4. Conclusions

In this study, the effect of some micro structural features on the cracking behavior of duplex stainless steels was investigated. The outcome can be summarized as follows;

Specimen hardness and yield stress were increased with ageing time mainly due to ferrite embrittlement.

Pop-in took place for those specimens aged for longer times.

The majority of the tested specimens showed invalidity for  $K_{IC}$  measurement.

The CTOD was affected by the specimen yield stress.

For longer ageing times, the CTOD value obtained by applying the standard BS7448 was similar to that obtained by the dcpd technique.

For shorter ageing times, below 850MPa yield stress, the CTOD value measured by BS7448 showed high value to that measured by the dcpd technique.

Fracture took place by ferrite cleavage and austenite tearing.

## References

- [1] J. O. Nilsson, Super Duplex Stainless Steel, Materials Science and Technology, Vol. 8, August 1992, 685-700.
- [2] L. J. R. Cohen, J. A. Charles and G. C. Smith, Influence of Cathodic Hydrogen On microstructure of duplex stainless steels Duplex Stainless Steels '87, Conf. Proc., York, Sep. 1987, Pub. I. O. M, 1988, 363-374.
- [3] S. Bonnet, J. Bourgoïn, J. Champredonde, D. Guttman and M. Guttman, Relationship Between Evaluation Of Mechanical Properties Of Various Cast Duplex Stainless Steels And Metallurgical And Aging Parameters: Outline of Current EDF Programmes, Mater. Sci. Tech., Vol. 6, 1990, 221-229.
- [4] R. O. Ritchie and A. W. Thompson, On Macroscopic And Microscopic Analysis For Crack Initiation And Crack Growth Toughness In Ductile Alloys, Metallurgical Transaction, Vol. 16A, 1985, 233-248.
- [5] ASTM E 1290, Standard Test Method For Crack-Tip Opening Displacement (CTOD) Fracture Toughness Measurement, Annual Book Of ASTM Standard, 1989.
- [6] BS 7448, Fracture Mechanics Toughness Tests. Part 1. Method For Determination of K<sub>IC</sub>, Critical CTOD and Critical J Values of Metallic Materials, Annual Book Of BSI Standard, 1991.
- [7] D. A. Curry, Cleavage Micromechanisms of Crack Extension In Steels, Metals Sci., Vol. 14, 1980, 319-326.
- [8] R. O. Ritchie and J. F. Knott, On The Relationship Between Critical Tensile Stress And Fracture Toughness In Mild Steel, J. Mech. Phys. Solids, Vol. 21, 1973, 395-410.
- [9] T. J. Marrow, A. O. Humphreys and M. Strangwood, The Crack Initiation Toughness For Brittle Fracture Of Super Duplex Stainless Steel, Fatigue & Fracture of Engineering Materials & Structures, Vol. 20. No. 7, 1997, 1005-1014.
- [10] J. R. Rice and M. A. Johnson, The Role of Large Crack Tip Geometry in Plane Strain Fracture, In: Inelastic Behaviour of Solids, McGraw Hill, 1970, 641-672.
- [11] T. J. Marrow and C. Harris, The Fracture Mechanism of 475°C Embrittlement in A Duplex Stainless Steels, Fatigue & Fracture of Engineering Materials & Structures, Vol. 19, No. 7, 1996, PP 935-947.
- [12] Cem Örneke, Safwan A. M. Idris, Pierfranco Reccagni and Dirk L. Engelberg, "Atmospheric-Induced Stress Corrosion Cracking of Grade 2205 Duplex Stainless Steel—Effects of 475 °C Embrittlement and Process Orientation Metals", Metals, Vol. 6, 2016, P 167.