

# A review on structures of secondary wall in reaction wood fiber of hardwood species

Rubaiyat Sharmin Sultana<sup>1,\*</sup>, Md. Mahabubur Rahman<sup>2</sup>

<sup>1</sup>Department of Botany, University of Rajshahi, Rajshahi 6205, Bangladesh

<sup>2</sup>Research Institute for Sustainable Humanosphere, Kyoto University, Kyoto 611-0011, Japan (Present address)

## Email address

sultanaru@yahoo.com (R. S. Sultana)

## To cite this article:

Rubaiyat Sharmin Sultana, Md. Mahabubur Rahman. A Review on Structures of Secondary Wall in Reaction Wood Fiber of Hardwood Species. *Plant*. Vol. 1, No. 5, 2013, pp. 54-59. doi: 10.11648/j.plant.20130105.12

---

**Abstract:** Due to a non-vertical orientation of the stem or branch, which may begin as responses of prevailing winds, snow, slope, or asymmetric crown shape, a specialized wood tissue forms, is called “reaction wood”. In hardwood species, the reaction wood tends to form on the upper side of a leaning stem or branch, is known to as “tension wood”. It is usually related with eccentric growth and changes in structure and chemistry of wood. During the formation of tension wood many changes found in wood cells, especially in wood fibers. The changes of wood properties in tension portion result different shrinkage characteristics during drying, creates a serious problem at adjacent portion of normal wood. However, tension wood is problematic in the hardwood industries and this wood is economically less valued. However, the studies on tension wood are necessary for beneficial applications in the wood industries sectors as well as research sectors. The knowledge on tension wood anatomy is still a matter for tree growers and timber processors, especially who are often involved in the furniture making. Besides, the understanding of tension wood formation provides a unique opportunity to obtain information on the molecular and biochemical mechanisms in the expression patterns of genes/proteins. The studies on reaction wood anatomy are not enough that we concluded any model. This review describes the features of fibers in tension wood to date, including secondary wall layers structure. Until date, six types structure of secondary cell wall layers for tension wood fibers such as,  $S_1 + S_2 + S_3 + G$ ,  $S_1 + S_2 + G$ ,  $S_1 + G$ ,  $S_1 + \bar{G}$ ,  $S_1 + S_2$ , and  $S_1 + S_2 + S_3$  have been reported, which considered being involved in plant evolution.

**Keywords:** Angiosperm, Cell Wall Layers, Microfibril Angle, Tension Wood, Wood Fiber

---

## 1. Introduction

Wood is a renewable natural resource, providing 1) timber for house building, furniture, packaging, 2) fibers for pulp, paper, plywood industries, and 3) firewood for energy. Furthermore, wood is a potential source of lignocellulose-based biofuels. Wood consists of different types of cell. Cell number and their arrangement differ depending on species [1-4]. Cells show two major functions in living trees: to provide a channel for water and minerals from the roots to the crown and to provide mechanical support for controlling the increasing mass of the tree. Besides, they contribute to tree growth over more than one year by storing temporary reserves. In most angiosperms, the roles have been separated with water travelling through specialized vessels, and support being provided by fibers, while parenchyma cells, organized in rays, are involved in the radial transfer of assimilates

between phloem and xylem.

A modification of wood at a portion in the leaning stem or branch can occur to withstand the pressure from the mass of the tree. Modifications of this structure enable branches to maintain their direction of growth against the force of gravity, or to enable stems forced nonvertical alignment to regain a vertical orientation. These latter occur variations in the wood properties, which are of benefit to the tree may also have negative economic consequences for the forestry and timber industries. By the cambium reactions in the response to a gravitational stimulus, leaning stems or branches formed modified wood with its special anatomical and chemical properties, is called “reaction wood” [5-13]. In angiosperm, reaction wood is generally formed on the upper side, and this wood is denoted as “tension wood” [14]. A mechanical stress of a large magnitude, known as “maturation stress” or “growth stress” [15, 16], occurs in the cell walls during the formation of

wood cells. This stress provides the tree with a motor system [17], necessary to maintain the stem at a constant angle during growth [18] or to achieve adaptive reorientations. In angiosperms, growth stress known as tensile stress [19], which also involved in the formation of tension wood. The involvement of plant hormones found in tension wood formation, is mainly regulated by auxins and gibberellic acid (GA). Joint effects of different classes of plant hormones or interactions among them may play crucial roles in the regulation mechanisms for tension wood [20].

The main problem of tension wood associated with the quality and utilization of wood and timber containing tension tissues is that their shrinkage characteristics are different from those of adjacent normal wood. Since tension wood is typically localized on one side (upper side) of the trunk, is often found only in the proportion of the total number of annual rings and it causes differential shrinkage effects during drying, which leads to warping, twisting, bending, and cracking of logs, planks, machined parts, and veneers. Warping and twisting of lumber containing tension wood is a serious problem of the hardwood industrial, particularly when the tension wood exists extensively at log. Collapse is another problem in wood industries associated with the seasoning of tension wood from the green condition [21]. Although some species have a greater tendency for collapse than others, the presence of tension wood aggravates this trend. For facilitated industrial utilization, it is very important to understand anatomical characteristics and wood properties in reaction wood. The presence of different characteristics in tension wood differs from the normal wood, especially tension characteristics in fiber. The secondary cell wall structure of tension fiber is one of the major characteristics. A large variations show within secondary cell wall structure of tension wood fibers, which will be a tool for establishment of evolutionary development of secondary wall structure in tension wood fiber for dicotyledons, and also be a source for studding origin and evolution of species.

Much effort has been put into reaction wood anatomy, wood properties, and wood chemistry considered to the commercial point of view. The purpose of this review is to introduce about features of fiber in reaction wood with respect to secondary wall structure which has recently taken on major importance in the minds of tree growers, timber users, and researchers involve in tension wood characterization and in evolutionary study on plant.

## 2. Tension Wood Characteristics

Tension wood is an abnormal wood formed typically on the upper side of branches and leaning or crooked stems of dicotyledonous trees. Tension wood differs from normal wood with the following main characteristics: i) Radial growth increment at upper side of leaning stem or branch is found in stem cross section [6, 18, 22, 23], ii) Green-sawn boards of tension wood are woolly surface [6], iii) Wider rings are found in tension wood zone [24], iv) The size and

number of vessels decrease with the formation of tension wood in generally [5, 25, 26], v) An internal gelatinous layer (G-layer) is present in tension wood fibers [5, 21, 27], which contains extensive  $\alpha$ -cellulose, is unlignified or less lignified and microfibrils in G-layer are oriented nearly parallel or parallel along the axis of the fiber [28, 29], vi) Particularly, tensile strength in tension wood is high, is found on upper side at either presence of G-layer [22, 30] or absence of G-layer [31] in tension fiber, vii) The microfibril angles in  $S_2$  layer of tension wood fiber are smaller than that of normal wood [25] and they are oriented nearly parallel or parallel in G-layer of the fiber [28, 29], and viii) Lignification of tension wood is lesser than normal wood [6,32-35].

## 3. Mechanisms for Tension Wood Formation


A mechanical stress of a large magnitude in tree known as "Maturation stress" or "growth stress" [15], which occurs in the cell walls during the formation of wood cells and provides the tree a motor system [17]. It is necessary to maintain the stem at a constant angle during growth [18] or to achieve adaptive reorientations. In angiosperms, a large tensile maturation stress (Maturation stress) is generated in the tension wood.

It is well known that the mechanism of tensile maturation stress has not been fully understood until date although the studies on the ultrastructure, chemical composition, molecular activity, mechanical state, and behavior of tension wood have been greatly stated. Different models have been proposed and discussed to explain the origin of the maturation stress [36-38]. During the maturation process, the specific organization of the G-layer suggests a tensile force induced in the microfibrils. this mechanism have been explained with different hypotheses, such as amorphous zones contract within the cellulosic microfibrils [39], microfibril aggregates form by the action of xyloglucans [37,40], and the effect of changes in moisture content was stimulated by pectin-like substances [36]. Goswami *et al.* [41] proposed an alternative model, who revealed that the maturation stress originates during cell maturation in the swelling of the G-layer and it transmits to the adjoining secondary layers, as a result the larger MFAs convert efficiently from lateral stress into axial tensile stress. The proposed model is not steady when the hygroscopic behavior of tension wood is discovered, which shrinks when it dries and not when it takes up water [22, 42, 43], this hypothesis focused attention on the possible role of cell wall layers other than the G-layer. Many types of wood fibers lacking a G-layer are known to produce axial tensile stress, such as normal wood [15] and the tension wood of many tropical species [5, 44, 45], so that mechanisms strictly depends on an action of the G-layer cannot provide a general explanation for the origin of tensile maturation stress in wood.


#### 4. Structure of Secondary Cell Wall Layer in Tension Wood Fiber

The plant cell wall in wood tissue has a multicomposite structure, consisting of several layers formed at different periods during cell differentiation. After the cell wall reaches its final size, the mechanically crucial secondary cell wall, consisting of three different layers such as  $S_1$ ,  $S_2$ , and

$S_3$  (Fig. 1, Fig. 2A) is formed [46]. The cellulose microfibril orientation and chemical composition varies among three layers of secondary cell wall. The  $S_2$  layer is the thickest (75%–85% of the total thickness of the cell wall) and most important for mechanical stability [47]. Between adjacent cells, a middle lamella layer attached to the primary cell wall ensures the adhesion of a cell to its neighbors (Fig. 1, Fig. 2A).

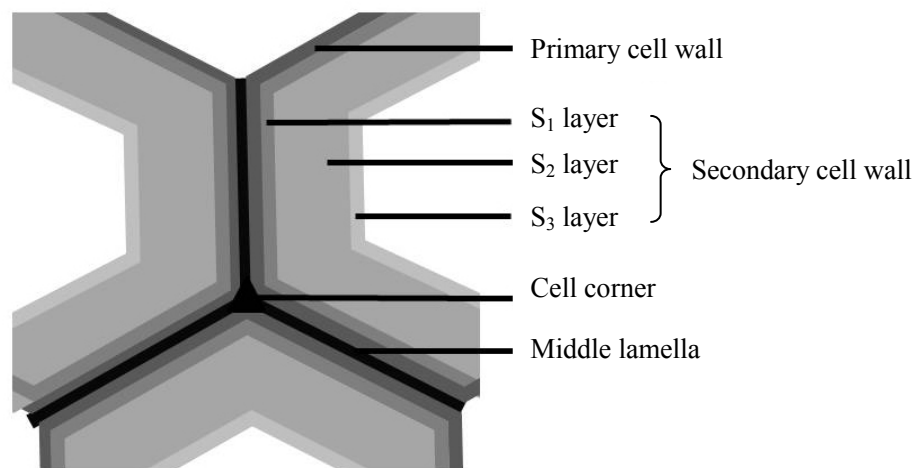

**Fig 1.** Diagrammatic figure of cell wall layers in normal wood fibers showing middle lamella, primary cell wall, secondary cell wall ( $S_1$ ,  $S_2$ ,  $S_3$  layers).

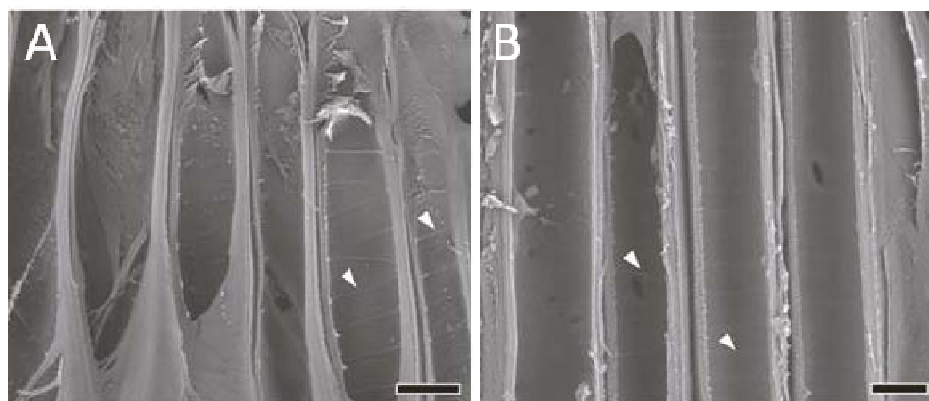

**Fig 2.** Scanning electron microphotographs of inner most layer of wood fibers. A) normal wood, B) tension wood. Both normal and tension wood fiber walls consist of  $S_3$  layers but lacks of G-layer; arrow heads, helical thickenings deposited on the  $S_3$  layer; bar = 10  $\mu\text{m}$ .


The chemical composition and the alignment of the cellulose microfibrils in fiber walls show significant different within interspecies and intraspecies variability [6, 48]. Similarly, structures of secondary cell wall in fibers are also significantly differed between normal and tension wood [49]. The differences with respect to thickness in the secondary cell wall of tension fibers are remarkable although investigations are limited. Gierlinger and Schwanninger [49] reported that thickness of cell middle lamella (CML) and primary cell wall in tension fibers decrease. In contrast, no alteration in thickness of primary cell wall in tension fibers has been investigated by Côté and Day [6].

In tension wood fibers, secondary wall is characterized by a thick cell wall and a special cell wall layer, usually referred

to as G-layer, which is not found in normal wood fibers [6, 50–52]. During tension wood formation, usually the  $S_3$  layer replaced by the so-called G-layer [29]. In contrast, lacking of G-layer in tension wood fibers of some hardwood species is also observed which similar to secondary wall structure of normal wood fiber [23, 25, 26, 53]. Until date, six types of wall layer structures in secondary wall of tension wood fiber are found in different hardwood species, as shown in Fig. 3. In the species which are formed G-fiber or  $\bar{G}$ -fiber, the structures of the secondary cell wall have been classified as, i)  $S_1 + S_2 + S_3 + G$  structured secondary wall: after formation of  $S_1$ ,  $S_2$ ,  $S_3$  layers, additionally G-layer is formed as a innermost layer where  $S_3$  layer is partially altered with G-layer [6, 21], ii)  $S_1 + S_2 + G$  structured secondary wall: G-layer is formed after development of  $S_1$  and  $S_2$  layers,

where  $S_3$  layer entirely replaced with G-layer [5, 6, 21, 22, 27, 30], iii)  $S_1 + G$  structured secondary wall: G-layer is developed after formation of  $S_1$  layer and it develops rapidly instead of  $S_2$  and  $S_3$  layers during high growth stress condition [21, 6], iv)  $S_1 + \dot{G}$  structured secondary wall:  $\dot{G}$ -layer is formed after generation of  $S_1$  layer and  $S_2$  or  $S_3$  layers are entirely lacking. It is characterized by unligified, porous, and microfibrils in  $\dot{G}$ -layer is oriented parallel to fiber axis. The presence of  $\dot{G}$ -layer has first reported by Araki *et al.*, [54] in tension wood of *Cercidiphyllum japonicum*, *Cornus controversa*, and *Alnus pendula* (Fig. 3). In the species which are lacked G-fiber or  $\dot{G}$ - fiber, the structure of the cell wall layer of tension wood fiber has been classified as, v)  $S_1 + S_2$  structured secondary wall: without formation of G-layer or  $S_3$  layer was observed during

complete maturation of wood fiber. The lack of  $S_3$  layer in reaction wood fiber without G-layer has been demonstrated by earlier studies in some species: *Magnolia obovata* and *M. kobus* [25], *Liriodendron tulipifera* [53], and *Osmanthus fragrans* [26]. This type of secondary wall structure usually is found in primitive angiosperms [25]. In these species, the microfibrils were oriented in a Z helix at the innermost part of the  $S_2$  layers, vi)  $S_1 + S_2 + S_3$  structured secondary wall: this three-layered secondary wall structure is similar to the wall structure of normal wood fiber. Usually,  $S_1$  layer is formed first and following  $S_2$  and  $S_3$  layers are deposited in the inner side of fiber cell lumen. Recently, we [23] reported this structure in reaction wood fiber without a G-layer for the first time (Fig. 2, Fig. 2B).

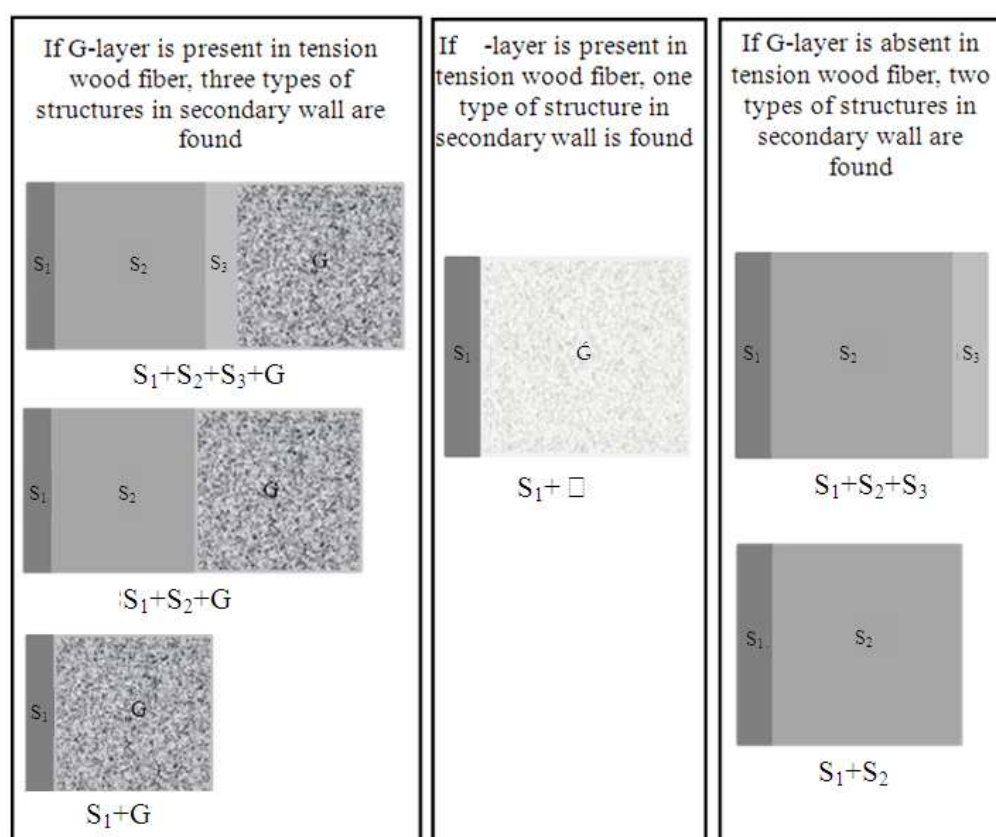

**Fig 3.** Diagrammatic figure shows different six types of secondary wall structure in tension fiber either with G-,  $\dot{G}$ -layer or without G-layer. Secondary wall of normal wood fiber generally composed of  $S_1$ ,  $S_2$ ,  $S_3$  layers, but due to formation of reaction wood, secondary wall composes with the different types of structure.

## 5. Conclusions

Accompanying the formation of tension wood, there are several alterations found in the wood cells, especially in wood fiber. The changes in secondary wall structure of tension wood fiber are noticeable among all changes. The alterations in the secondary cell wall structure of tension wood fiber are often classified into six types,  $S_1 + S_2 + S_3 + G$ ,  $S_1 + S_2 + G$ ,  $S_1 + G$ ,  $S_1 + \dot{G}$ ,  $S_1 + S_2$ , and  $S_1 + S_2 + S_3$ . One type of secondary cell wall structure among six types is formed in one species during tension wood formation.

Therefore, one type of secondary cell wall structure is an identified character for one species. The variations in secondary cell wall structure in tension wood fiber is an potential tool to establish an evolutionary development of secondary wall structure of tension wood fiber for dicotyledons, and to illustrate origin and evolution of species, as described previously in the evolutionary development of vessel elements [55] and wood rays [56] of dicotyledons. The review stated here will helpful for researcher involved studies on tension wood as well as evolution of plant.

## References

- [1] Jane FW. 1970. The Structure of Wood. Adam and Charles Black, London.
- [2] Core HA, Côté WA and Day AC. 1979. Wood Structure and Identification. Syracuse University Press, Syracuse, New York.
- [3] Butterfield BG and Meylan BA. 1980. Three Dimensional Structure of Wood: An Ultrastructural Approach. Chapman and Hall, London.
- [4] Wilson K and White DJB. 1986. The Anatomy of Wood, its Diversity and Variability. Stobart, London.
- [5] Onaka F. 1949. Studies on compression and tension wood. Wood Res., 1: 1–88 (in Japanese).
- [6] Côté WA Jr and Day AC. 1965. Anatomy and ultrastructure of reaction wood. In W.A.Jr. Côté (ed.), *Cellular ultrastructure of woody plants*. Syracuse University Press, New York., 391–418.
- [7] Wardrop AB. 1965. The formation and function of reaction wood. In W.A.Jr. Côté (ed.), *Cellular ultrastructure of woody plants*, Syracuse University Press, New York, 371–390.
- [8] Scurfield G. 1973. Reaction wood: its structure and function. *Science*, 179: 647–655.
- [9] Wilson BF and Archer RR. 1977. Reaction wood: Induction and mechanical action. *Annual Review of Plant Physiology*, 28: 23–43.
- [10] Fisher JB and Stevenson JW. 1981. Occurrence of reaction wood in branches of dicotyledons and its role in tree architecture. *Botanical Gazette*, 142: 82–95.
- [11] Timell TE. 1986a. Compression wood in gymnosperms I. Springer-Verlag, Berlin New York.
- [12] Timell TE. 1986b. Compression wood in gymnosperms II. Springer-Verlag, Berlin New York.
- [13] Timell TE. 1986c. Compression wood in gymnosperms III. Springer-Verlag, Berlin New York.
- [14] International Association of Wood Anatomists. 1964. Multilingual glossary of terms used in wood anatomy. Winterthur, Verlagsanstalt Buchdruckerei Konkordia.
- [15] Archer RR. 1986. Growth Stresses and Strains in Trees. Springer Verlag, Berlin.
- [16] Fournier M, Chanson B, Thibaut B and Guitard D. 1991. Mechanics of standing trees: modelling a growing structure submitted to continuous and fluctuating loads. 2. Tridimensional analysis of maturation stresses. Case of standard hardwood. *Annals of Forest Science*, 48: 527–546.
- [17] Moulia B, Coutand C and Lenne C. 2006. Posture control and skeletal mechanical acclimation in terrestrial plants: implications for mechanical modeling of plant architecture. *Am. J. Bot.*, 93: 1477–1489.
- [18] Alme'ras T and Fournier M. 2009. Biomechanical design and long-term stability of trees: morphological and wood traits involved in the balance between weight increase and the gravitropic reaction. *J. Theor. Biol.*, 256: 370–381.
- [19] Bowling AJ and Vaughn KC. 2009. Gelatinous fibers are widespread in coiling tendrils and twining vines. *Am. J. Bot.*, 96: 719–727.
- [20] Du S and Yamamoto F. 2007. An overview of the biology of reaction wood formation. *J. Integrat. Plant Biol.*, 49(2): 131–143.
- [21] Dadswell HE and Wardrop AB. 1955. The structure and properties of tension wood. *Holzforchung*, 9:97–104.
- [22] Fang C-H, Clair B, Grill J and Liu S-Q. 2008. Growth stresses are highly controlled by the amount of G-layer in poplar tension wood. *IAWA J.*, 29(3): 237–246.
- [23] Sultana RS, Ishiguri F, Yokota S, Iizuka K, Hiraiwa T and Yoshizawa N. 2010. Wood anatomy of nine Japanese hardwood species forming reaction wood without gelatinous fibers. *IAWA J.*, 31(2): 191–202.
- [24] Hillis WE, Evans R and Washusen R. 2004. An unusual formation of tension wood in a natural forest *Acacia* sp. *Holzforchung*, 58: 241–245.
- [25] Yoshizawa N, Inami A, Miyake S, Ishiguri F and Yokota S. 2000. Anatomy and lignin distribution of reaction wood in two *Magnolia* species. *Wood Science and Technology*, 34: 183–196.
- [26] Hiraiwa T, Yamamoto Y, Ishiguri F, Iizuka K, Yokota S and Yoshizawa N. 2007. Cell wall structure and lignin distribution in the reaction wood fiber of *Osmanthus fragrans* var. *aurantiacus* Makino. *Cellulose Chemistry and Technol.*, 41: 537–543.
- [27] Saiki H and Ono K, 1971. Cell wall organization of gelatinous fibers in tension wood. *Bull. Kyoto Univ. For.*, 43: 210–217.
- [28] Fujita M, Saiki H and Harada H. 1974. Electron microscopy of microtubules and cellulose microfibrils in secondary wall formation of poplar tension wood fibers. *Mokuzai Gakkaishi*, 20: 147–156.
- [29] Norberg PH and Meier H. 1966. Physical and chemical properties of the gelatinous layer in tension wood fibres of aspen (*Populus tremula* L.). *Holzforchung*, 20: 174–178.
- [30] Okuyama T, Yamamoto H, Iguchi M and Yoshida M. 1990. Generation process of growth stresses in cell walls II: Growth stresses in tension wood. *Mokuzai Gakkaishi*, 36: 797–803.
- [31] Okuyama T, Yamamoto H, Yoshida M, Hattori Y and Archer RR. 1994. Growth stresses in tension wood: Role of microfibrils and lignification. *Annals of Forest Science*, 51: 291–300.
- [32] Timell TE. 1969. The chemical composition of tension wood. *Svensk Papperstidning*, 72: 173–181.
- [33] Sarkanen KV and Hergert HL. 1971. Classification and distribution. In KV Sarkanen, CH Ludwig (eds.), *Lignins: Occurrence, formation, structure and reaction*, Wiley-Interscience Press, New York, 1–18.
- [34] Sugiyama K, Okuyama T, Yamamoto H and Yoshida M. 1993. Generation process of growth stresses in cell walls: relation between longitudinal released strain and chemical composition. *Wood Science and Technology*, 27: 257–262.
- [35] Baba K, Ona T, Takabe K, Itoh T and Ito K. 1996. Chemical and anatomical characterization of the tension wood of

*Eucalyptus camaldulensis* L. *Mokuzai Gakkaishi*, 42: 795-798.

- [36] Bowling AJ and Vaughn KC. 2008. Immunocytochemical characterization of tension wood: gelatinous fibers contain more than just cellulose. *Am. J. Bot.*, 95: 655–663.
- [37] Mellerowicz EJ, Immerzeel P and Hayashi T. 2008. Xyloglucan: the molecular muscle of trees. *Ann. Bot. (Lond)*, 102: 659–665.
- [38] Okuyama T, Yoshida M and Yamamoto H. 1995. An estimation of the turgor pressure change as one of the factors of growth stress generation in cell walls: diurnal change of tangential strain of inner bark. *Mokuzai Gakkaishi*, 41: 1070–1078.
- [39] Yamamoto H. 2004. Role of the gelatinous layer on the origin of the physical properties of the tension wood. *J. Wood Sci.*, 50: 197–208.
- [40] Nishikubo N, Awano T, Banasiak A, Bourquin V, Ibatullin F, Funada R, Brumer H, Teeri TT, Hayashi T and Sundberg B. 2007. Xyloglucan endo-transglycosylase (XET) functions in gelatinous layers of tension wood fibers in poplar: a glimpse into the mechanism of the balancing act of trees. *Plant Cell Physiol.*, 48: 843–855.
- [41] Goswami L, Dunlop JWC, Jungnikl K, Eder M, Gierlinger N, Coutand C, Jeronimidis G, Fratzl P and Burgert I. 2008. Stress generation in the tension wood of poplar is based on the lateral swelling power of the G-layer. *Plant J.*, 56: 531–538.
- [42] Clair B, Gril J, Di Renzo F, Yamamoto H and Quignard F. 2008. Characterization of a gel in the cell wall to elucidate the paradoxical shrinkage of tension wood. *Biomacromolecules*, 9: 494–498.
- [43] Clair B and Thibaut B. 2001. Shrinkage of the gelatinous layer of poplar and beech tension wood. *IAWA J.*, 22: 121–131.
- [44] Ruelle J, Yamamoto H and Thibaut B. 2007. Growth stresses and cellulose structural parameters in tension and normal wood from three tropical rainforest angiosperm species. *Bio Resources*, 2: 235–251.
- [45] Clair B, Ruelle J, Beauchêne J, Prevost MF and Djimbi MF. 2006. Tension wood and opposite wood in 21 tropical rain forest species. 1. Occurrence and efficiency of the G-layer. *IAWA J.*, 27: 329–338.
- [46] Plomion C, Leprovost G and Stokes A. 2001. Wood formation in trees. *Plant Physiol.*, 127: 1513–1523.
- [47] Fengel D and Wegener G. 1989. *Wood: Chemistry, Ultrastructure, Reactions*. Walter de Gruyter and Co., Berlin.
- [48] Barnett JR and Bonham VA. 2004. Cellulose microfibril angle in the cell wall of wood fibres. *Biological Rev.*, 79: 461–472.
- [49] Gierlinger N and Schwanninger M. 2006. Chemical Imaging of Poplar Wood Cell Walls by Confocal Raman Microscopy. *Plant Physiol.*, 140: 1246–1254.
- [50] Côté, WA, Day AC and Timell TE. 1969. A contribution to the ultrastructure of tension wood fibres. *Wood Science and Technology*, 3: 257–271.
- [51] Araki N, Fujita M, Saiki H and Harada H. 1982. Transition of fiber wall structure from normal wood to tension wood in *Robinia pseudoacacia* L. and *Populus euramericana* Guinier. *Mokuzai Gakkaishi*, 28: 267-273.
- [52] Mukogawa Y, Nobuchi T and Sahri MH. 2003. Tension wood anatomy in artificially induced leaning stems of some tropical trees. *Forest Research, Kyoto*, 75: 27-33.
- [53] Yoshida M, Okuda T and Okuyama T. 2000. Tension wood and growth stress induced by artificial inclination in *Liriodendron tulipifera* Linn. and *Prunus spachiana* Kitamura f. *ascendens* Kitamura. *Annals of Forest Science*, 57: 739-746.
- [54] Araki N, Fujita M, Saiki H and Harada H. 1983. Transition of fiber wall structure from normal wood to tension wood in certain species having gelatinous fibers of S<sub>1</sub> + G and S<sub>1</sub> + S<sub>2</sub> + S<sub>3</sub> + G types. *Mokuzai Gakkaishi*, 29: 491-499.
- [55] Dickison WC. 2000. Evolutionary, physiological, and ecological plant anatomy. In: W.C. Dickison (ed.), *Integrative plant anatomy*, Elsevier, San Diego, California, USA., 203-332.
- [56] Kribs DA. 1935. Salient lines of structure specialization in the wood rays of dicotyledons. *Botanical Gazette*, 96: 547-556.